

# 行政院國家科學委員會專題研究計畫 期中進度報告

## 子計畫四：金屬氧化物的結構與晶格形變的 X 光散射研究

(2/3)

計畫類別：整合型計畫

計畫編號：NSC94-2112-M-032-002-

執行期間：94 年 08 月 01 日至 95 年 07 月 31 日

執行單位：淡江大學物理學系

計畫主持人：杜昭宏

報告類型：精簡報告

處理方式：本計畫可公開查詢

中 華 民 國 95 年 5 月 27 日

# 行政院國家科學委員會補助專題研究計畫期中報告

過度金屬及硫屬化合物之物性研究與應用

子計畫四：金屬氧化物的結構與晶格形變的 X 光散射研究(2/3)

計畫類別：  個別型計畫       整合型計畫

計畫編號：NSC 93-2112-M-032-002-

執行期間： 94 年 8 月 1 日至 95 年 7 月 31 日

計畫主持人： 杜昭宏 助理教授

共同主持人：

計畫參與人員：

本成果報告包括以下應繳交之附件：

- 赴國外出差或研習心得報告一份
- 赴大陸地區出差或研習心得報告一份
- 出席國際學術會議心得報告及發表之論文各一份
- 國際合作研究計畫國外研究報告書一份

執行單位：淡江大學物理系

中 華 民 國      95 年      5 月      17 日

## 一、 摘要

本計畫第二期的主要目的是要測試在上年度所設立的高解析度(high-resolution)及高輝度(brilliance)的三軸四環 X-光繞射儀，並用其來研究金屬氧化物中由電子及晶格擾動所產生的有序調制結構(modulated structure)，及其他金屬氧化物塊材、薄膜之結構分析，並配合使用同步輻射 X-光共振散射(resonant x-ray scattering)，來進一步了解這些調制結構的電子及磁結構在外加電場及磁場下的物理特性。

**關鍵詞：**X-光散射，過度金屬氧化物，硫化物，調制結構，晶格形變

### Abstract

In the first year, I completed the setup of a triple-axes and 4-circle diffractometer for the studies of x-ray scattering on single crystals and thin films at low temperature. Following to the completion of the in-house facility, we have carried out the preliminary measurements on many oxides systems, such as  $\text{BaRuO}_3$ ,  $\text{La}_{2-x}\text{Sr}_x\text{NiO}_4$ ,  $\text{K}_{0.3}\text{MoO}_3$ , and  $\text{Rb}_x\text{WO}_{3\pm y}$ . In addition, we also performed the synchrotron X-ray scattering on  $\text{BaRuO}_3$  and  $\text{K}_{0.3}\text{MoO}_3$  to further study the modulations related electronic and the magnetic structures.

**Key words:** transition metal oxides, static modulation, synchrotron x-ray scattering

## 二、 緣由與目的

There exist many condensed materials in which the charge degrees of freedom form regular spatial patterns commonly known as “stripes”. These stripe-like modulated structures typically result from the competition between the short-range attractive forces, which give rise to a condensed phase, and the largely unscreened, the long-range Coulomb interactions. Specifically, in the condensed phase and in the absence of long-range repulsive forces between charges, the charge degrees of freedom tend to form clumps that are to phase separate. This tendency to phase separation is frustrated by the long-range repulsive Coulomb interactions, and results in the spontaneous organization of the charge degrees of freedom in low-dimensional structures. Such stripe-like modulations have been recently observed experimentally in a large class of strongly correlated electrons systems, i.e., doped Mott insulators such as the copper oxides, the nickelates, and the manganates, and demonstrated to play an important role on the transport behaviour. For instance, in the cuprate family, the holes doped into the  $\text{CuO}_2$  planes can order in an array of periodically spaced stripes which separate antiferromagnetic domains, which has been observed using inelastic neutron scattering and been interpreted as dynamic stripes [9]. The transport measurements also evidence that the electronic state of high- $T_C$  superconductors possesses

the anisotropic characteristic.

Based on the experimental findings, anisotropic and static/dynamic charge inhomogeneity, Kivensson and Emery further proposed that there should exist electronic quantum liquid-crystal phases in those highly correlated electron systems, namely the stripe liquid phases [10], and these electronic liquid phases can be superconducting or insulating at low temperatures. Since then, there are many theoretical models devoting to the studies of the correlations of the spin and charge liquid states and the superconductivity [10, 11], but the experimental evidences are of lack because of the difficulties in probing the stripe liquid phases using high-resolution neutron or x-ray scattering.

Analogous to the classical liquid crystals which break spontaneously the rotation and/or translation symmetries of free space, and resulting in the nematic, smectic, and isotropic phases, the proposed electronic liquid crystals are quantum analogous of these phases, i.e., the nematic stripes, the smectic stripes, and the isotropic stripes phases. Both x-ray and neutron scattering are the ideal probes for directly studying the modulations. Neutron scattering is sensitive to the dynamic or static magnetic structures, but it loses the sensitivity to the charge and the spatial resolution. Contrast to neutron scattering, x-ray is more sensitive to the charge modulation and with a higher spatial resolution (typically it can be as high as  $10^{-4} \text{ \AA}^{-1}$ ), so x-ray scattering is suitable for probing the static nematic, smectic and isotropic charge liquid phases, and the coupling of the modulations and the lattice. In order to study the fields effects on the stripes liquid phases and the coupling interactions of the lattice and the modulations, two strongly correlated electron systems, nickelites,  $\text{La}_{2-x}\text{Sr}_x\text{NiO}_4$ , and ruthenate,  $\text{BaRuO}_3$ , will be used as the studying materials.

This proposal aims at studying the dynamic behaviour of the electronic liquid phases as that observed in  $\text{La}_{2-x}\text{Sr}_x\text{NiO}_4$  under the application of electric and magnetic fields and the lattice distortions in the ruthenate  $\text{BaRuO}_3$  using x-ray scattering. As the modulated structures and the lattice distortions are the common characteristics in many transition metal oxides, therefore, the studies and the characterization of the structures of the newly synthesized metal oxides by other sub-groups are also the target of this proposal.

### 三、 結果與討論

The homogeneous phase in low dimensional materials, such as  $\text{K}_{0.3}\text{MoO}_3$ ,  $\text{NbSe}_3$ ,  $2\text{H-NbSe}_2$  and TMTSF molecules, undergo a phase transition to charge density waves (CDWs) at low temperatures. The instability toward spontaneous formation of charge-density modulations is driven by electron-phonon interactions, or electron-electron [1]. Among many other

interesting aspects of CDW, transport property has attracted lots of attentions from both experimental and theoretical sides. It is generally believed that the current is suppressed at small biased voltage, where the CDW is pinned by impurity potential. Above some threshold voltage, the sliding motion along the applied electric field starts and the current increases significantly. It has been known that this dynamic behaviour involves the phase slippage of the density waves [2]. In addition, the dynamics of the disordered state driven by an external force in a periodic media is also of the characteristic in common in many physical systems, such as the density waves and the vortex lattices [3].

An interesting question naturally arises: How does the internal structure of density modulations change in the presence of the applied electric field? In particular, in the non-equilibrium sliding motion, the robust periodic structure, originally developed in static limit, might become unstable. In this report, we address this issue by applying the techniques of multiple (three-wave) X-ray diffraction and x-ray scattering to measure the changes in the CDW lattice and its internal structure with respect to the applied electric fields. From the extracted phase  $\delta_3(V)$  of the three-wave diffraction and the peak profile of the CDW satellite reflection, we demonstrate that the occurrence of nonlinear conductivity caused by the periodic media is through the internal deformation of the CDW lattice, i.e., a phase jump of  $2\pi$ , as the applied voltage exceeding the threshold. From the evolution of the measured peak width of satellite reflections as a function of the field strength, we also report that the CDW lattice can be driven to move and undergo a dynamic phase transition from the disordered pinning state to ordered moving solid state and then to disordered moving liquid.

A good quality single crystal  $K_{0.3}MoO_3$  was first characterized and oriented at room temperature. The non-linear conductivity [4] was confirmed by measuring the  $I$ - $V$  curve at 70 K as shown in figure 1a, indicating the dynamic transition from the pinned CDWs to sliding motions at the threshold field  $V_C \approx 0.165$  V. It is noteworthy that the nonlinearity is not as robust as at low temperature due mainly to the thermal fluctuations smearing out the switching behavior.


The *in-situ* measurements were carried out on the Taiwan Beamline BL12B2 of Spring-8 synchrotron facility. The incident x-ray wavelength was selected to be 1Å. The satellite reflections signal the formation of CDW, located at the Bragg position  $G = (13 q 6.5)$ , where  $q \approx 0.748$ . Scans were performed through the longitudinal direction of  $[2 0 -1]$ , and the data was convoluted with the resolution function obtained from the nearby Bragg peak  $(12 0 -6)$ . Figure 1b shows the evolution of the peak width of CDW reflection as a function of applied voltage at  $T = 70$  K.

As shown in figure 1b, the FWHM of the satellite reflection,  $(13 q -6.5)$ , remains more or less

unchanged below the critical voltage  $V_c \approx 0.165$  V determined from the transport measurement. Above the critical voltage, where the CDW enters the sliding phase, the FWHM width decreases as predicted by previous theoretical investigations. As the voltage exceeding 0.18 V, the lattice shows a long-range ordered state; namely a moving solid phase [5]. This interesting dynamical narrowing of half width is a strong indication that the pinning forces due to random potentials become irrelevant (or less efficient) when the CDW starts to slide. When the voltage goes beyond 0.22 V, non-equilibrium effects, amplitude fluctuations and others become important and the Bragg peaks disappear. This is clearly evidenced by the sharp increase of FWHM.


The other key quantity we studied is the triplet phase  $\delta_3$  of a 3-wave multiple diffraction at different biased voltages. To set up a 3-wave  $(\mathbf{O}, \mathbf{G}_1, \mathbf{G}_2)$  multiple diffraction experiment, the crystal is first aligned for a primary reflection  $\mathbf{G}_1$ . It is then rotated around the reciprocal lattice vector  $\mathbf{G}_1$  with an azimuthal angle  $\psi$  to bring in the secondary reflection  $\mathbf{G}_2$  which also satisfies Bragg's law. Namely, both  $\mathbf{G}_1$  and  $\mathbf{G}_2$  reflections take place simultaneously.  $\mathbf{O}$  stands for the incident reflection. The interaction of the multiply diffracted waves modifies the intensity of the primary reflection. Intensity variation showing asymmetric distribution versus  $\psi$  gives the information about  $\delta_3$ , which is the triplet phase of  $F_{G_2}F_{G_3}/F_{G_1}$  involved in the 3-wave diffraction. Previously [6], we demonstrated that the triplet phase  $\delta_3$  due to the coupling between the CDW lattice and its host lattice can be probed using multiple diffraction. Here we further demonstrate that measuring the relative change in  $\delta_3$ ,  $\Delta\delta_3$ , caused by a driving force, makes the study of the internal deformation of the CDW lattice possible.

Through the azimuthal scan around the primary reflection  $\mathbf{G}_1 = (13 \mathbf{q} -6.5)$  at  $T = 70$  K, we obtained the three-wave diffraction pattern containing lots of multiple diffraction peaks. We concentrated, here, only on the particular three-wave diffraction,  $(0 \ 0 \ 0)$ ,  $(13 \mathbf{q} -6.5)$  and  $(4 -8 \ 4)$  at  $\psi = 108.53^\circ$ , where the primary reflection is  $(13 \mathbf{q} -6.5)$  and the coupling reflection is  $(9 \ 8 + \mathbf{q} \ 10.5)$ . The profile asymmetry of the diffraction intensity of  $(13 \mathbf{q} -6.5)$  versus  $\psi$  at  $V = 0$  is typical for  $\delta_3 = 0$ . The phase variation  $\Delta\delta_3$  due to non-zero applied voltages was analyzed based on the dynamical theory for multiple diffractions [7]. In Fig. 2, the profile develops different asymmetry at different finite voltages. In the static CDW state, the crystal lattice possesses a centrosymmetric structure, and a change in the peak profile means that this centrosymmetry is broken due to the relative motion of ions by a driving force. This results in a non-zero of  $\Delta\delta_3$ , suggesting the internal deformation of the original charge density distribution by the driving force. As shown in figure 1c, The estimated  $\Delta\delta_3$  from curve fitting at 0.1, 0.12, 0.13, 0.14, 0.15, and 0.16 V are about  $6^\circ$ ,  $10^\circ$ ,  $18^\circ$ ,  $17^\circ$ ,  $17^\circ$ , and  $10^\circ$  respectively, and then back to  $0^\circ$  for  $V > 0.18$  V. This evidences experimentally that the occurrence of non-linear transport behavior is through a phase jump of  $2\pi$  at the sliding threshold, i.e., from the pinned to sliding states [8].

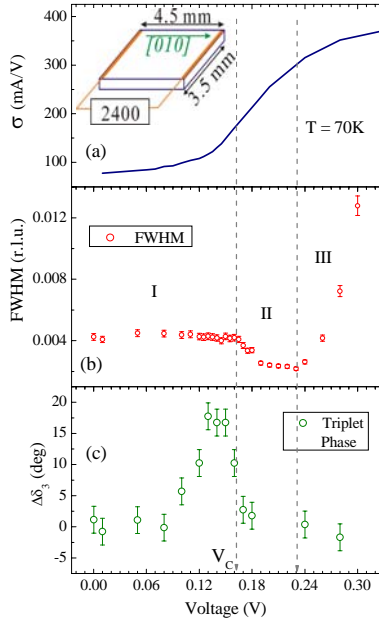

**Figure 1:** (a) Resistance versus voltage at 70 K. It shows the nonlinear behavior with a threshold voltage  $V_C \approx 0.165$  V. The inset shows the dimension of the sample and the experimental setup. (b) Evolution of the FWHM of the CDW satellite reflects as a function of applied voltage. One can classify CDW into three phases: (I) the creeping CDW state, (II) the moving solid and (III) the moving liquid. (c) The triplet phase  $\Delta\delta_3$  at different voltages. Note that, in the sliding phase,  $\Delta\delta_3 = 0$  is a direct evidence that the pinning forces become irrelevant.

In addition to the dynamic phase transition of CDW caused by the application of voltage on a low-dimensional material  $K_{0.3}MoO_3$ , we also carried out the measurement, using high-resolution synchrotron x-ray scattering, on a high- $T_C$  related compound  $La_{2-x}Sr_xNiO_4$ . On a high quality single crystal  $La_{5/3}Sr_{1/3}NiO_4$ , the satellite reflections due to the formation of charge stripes were located at positions  $(H\ 2q\ L)$ , where  $H$  is even,  $q \sim 0.33$ , and  $L = \text{integer}$ , with a transition temperature of  $\sim 240$  K. The charge stripes were observed to possess the characteristic of two-dimensional in nature and be a quenched disordered CDW state as shown in figure 2. Further, by the application of a driving force, current, we also observed that the charge stripes behave like the liquid crystal; i.e. the charge striped liquid. So far, this is just a preliminary study, the detailed measurements about this fascinating charge liquid state is still under going.

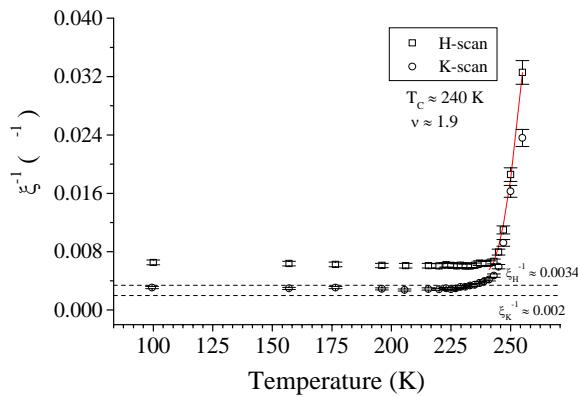

**Figure 2:** The evolution of correlation lengths along the H and K-direction. The dotted lines are the resolutions along the H and K directions respectively. It is clear to see that the charge stripes do not form a long range ordered state at low temperature, and the red line is the fit of a power law which gives a unusual high exponent  $\nu \sim 1.9$ . This behaviour suggests a quenched disordered charge stripes.

#### 四、 計畫成果自評

Using high-resolution x-ray scattering and x-ray multiple diffraction, we have demonstrated that the nonlinear conductivity due to the formation of density wave modulation is correspondent to the phase jump of  $2\pi$  at the boundary of the nonlinearity, and the modulated lattice can be driven to move as the applied field exceeding the threshold. In addition, an in-house x-ray source and a 4-circle diffractometer have also been set up for the x-ray scattering study of single crystals and highly orientated thin films in my laboratory, and we have helped the characterization of single crystals grown by other research groups. Stepping into the next year of this project, the studies of dynamic and static phase transitions of the modulations in transition metal oxides will be still carried out using synchrotron radiation source. The in-house facility will continue to serve other research groups.

**This part of results has been accepted for publication on Applied Physics Letter, volume 88, issue 24, 2006.**

#### 五、 參考文獻

- 1: A. W. Overhauser, Adv. Phys. 27, 343 (1978)
- 2: S. Brazovskii, *et al.* Phys. Rev B. 61, 10640 (2000).
- 3: U. Yaron, *et al.*, Nature 376, 753 (1995)
- 4: N. Ogawa, *et al.*, Phys. Rev. Lett. 87, 256401 (2001)
- 5: R. Danncau, *et al.*, Phys. Rev. Lett. 89, 106404 (2002)
- 6: C.-H. Du, *et al.*, Acta Cryst. A 60, 209 (2004)
- 7: S. L. Chang, X-ray multiple-wave diffraction: theory and application, Springer-Verlag, Berlin, (2004); R. Colella, Acta Crystallogr. A 30, 413 (1974); Q., Shen, Phys. Rev. Lett. 80, 3268 (1998)
- 8: A letter for this experiment has been submitted to APL. A report has been published on cond-mat/0412696.
- 9: J. M. Tranquada, *et al.*, Nature, 375, 561, 1995; S.-W. Cheong, *et al.*, Phys. Rev. Lett. 67, 1791, 1991; K. Yamada, *et al.*, Phys. Rev. B 57, 6165, 1998; H. A. Mook, *et al.*, Nature 395, 580, 1998
- 10: S. A. Kivelson, E. Fradkin and V. J. Emery, Nature, 393, 550, 1998; V. J. Emery, *et al.*, Phys. Rev. Lett. 85, 2160, 2000; T. Bellini, *et al.*, Phys. Rev. Lett. 88, 245506, 2002
- 11: S.-H. Lee, *et al.*, Phys. Rev. Lett. 88, 126401, 2002